



Interference fit effect on improving fatigue life of a holed single plate

D. Croccolo

DIEM, University of Bologna, Bologna (Italy)

dario.croccolo@unibo.it

M. De Agostinis

DIEM, University of Bologna, Bologna (Italy)

m.deagostinis@unibo.it

N. Vincenzi

DIEM, University of Bologna, Bologna (Italy)

nicolo.vincenzi@unibo.it

ABSTRACT. This paper deals with the influence of interference fit coupling on the fatigue strength of holed plates. The effect was investigated both experimentally and numerically. Axial fatigue tests have been carried out on holed specimens made of high performance steel (35KB2, 1075MPa of Ultimate strength and 990MPa of Yield strength) with or without a pin, made of the same material, press fitted into their central hole. Three different conditions have been investigated: the open hole specimens, specimens with 0.6% of nominal specific interference and specimens with 2% of nominal specific interference. The experimental stress-life (S–N) curves pointed out an increased fatigue life of the interference fit specimens compared with the open hole ones. The numerical investigation was performed in order to analyse the stress field by applying an elastic plastic 2D simulation with commercial Finite Element software. The stress history and distribution around the interference fitted hole, indicates a significant reduction of the stress amplitude produced by the external loading (remote stress) since a residual and compressive stress field is generated by the pin insertion.

SOMMARIO. In questo lavoro è stata analizzata l'influenza di un accoppiamento per interferenza sulla resistenza a fatica di piastre forate. L'effetto è stato studiato sia sperimentalmente sia numericamente. Le prove di fatica sono state condotte su provini forati in acciaio ad alte prestazioni (35KB2, 1075MPa di sollecitazione massima e 990MPa di snervamento) con o senza un perno dello stesso materiale, inserito per interferenza nel foro centrale. Tre diverse condizioni dei provini sono state studiate: provini con foro libero, provini con 0,6% d'interferenza specifica nominale generata dal perno e provini con 2% di interferenza specifica nominale generata dal perno. La curva di vita a fatica (S-N) ottenuta ha evidenziato un'influenza positiva dell'interferenza sulla resistenza a fatica dei provini. L'indagine numerica è stata realizzata al fine di calcolare lo stato di deformazione e sollecitazione in campo elasto-plastico su una geometria semplificata 2D del provino in esame; allo scopo è stato impiegato un software commerciale agli elementi finiti. La storia di carico e la distribuzione delle sollecitazioni intorno al foro generato sia dall'interferenza sia dal carico esterno applicato, mostra una significativa riduzione dell'ampiezza della sollecitazione nel caso di interferenza dovuta alla presenza di tensioni residue di compressione.

KEYWORDS. Fatigue, interference-fit, holed single plate

INTRODUCTION

The failure of mechanical components is mainly caused by the fatigue stresses especially in the presence of geometric variations such as the holes realised in order to join two different parts, for instance, with bolts or pins [1]. In the case of bolts connections the holes have, normally, a clearance coupling with the shank of bolts because the connection leverages the friction forces generated between the mating parts [2]. On the other hand the pins connections (shaft-hub connections) can be realised with different amount of interference level [3]. The holes cause a geometrical discontinuity, which leads to stress concentration during the loading; furthermore, the drilling operation creates rough surfaces or damages so that the fatigue life of component may be drastically reduced. Such situation forces a compensation of the fatigue life reduction that can be obtained with different techniques such as the cold expansion or the interference fit connections. The present paper aims at investigating the effect of interference fit level on the fatigue life of holed plates which are used in caterpillar chain of high power excavators (Fig. 1). The meshes of the chain are, indeed, linked together by means of pins axially inserted and joined with a stated interference level; since some dangerous failures occurred in field tests, it was decided to investigate the relation between the amount of interference and the fatigue life of such components. There are a lot of studies concerning the effect of interference fit on the fatigue life [4-8]; anyway these papers are mainly dedicated to the study of aluminium alloys (2xxx and 7xxx series) or the direct effect of interference fit is shadowed by either cold expansion or bolt clamping effect. On the opposite the material investigated in this paper is high strength steel so that no previous tests or results can be found concerning this application.

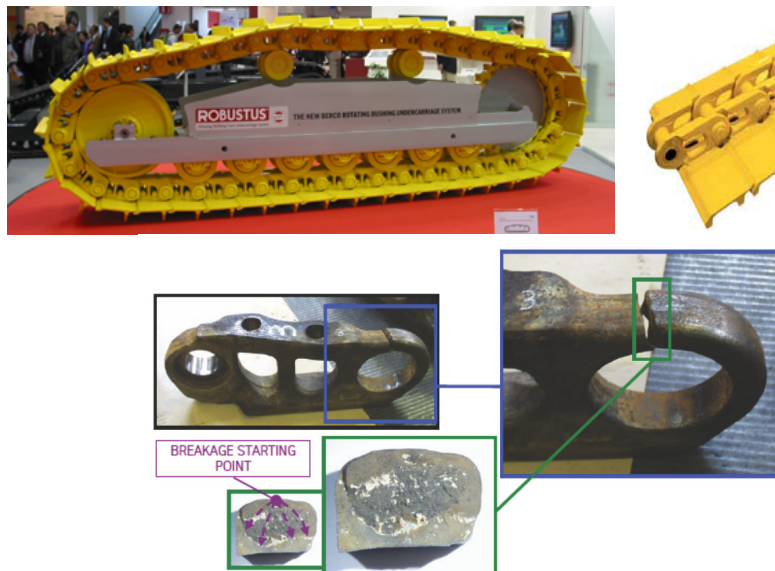


Figure 1: Caterpillar chain of high power excavator with some dangerous failures occurred on the chain mesh.

EXPERIMENTAL METHODS AND TOOLS

The specimens are reported in the draft of Fig. 2. They were cut from the real component (the real mesh) and machined in order to obtain the actual dimension (160mm high, 18mm width and 4mm of thickness with a hole diameter $D=5\text{mm}$).

The material properties are the following: Ultimate stress 1075MPa, Yield point 990MPa, Young modulus 209GPa, slope of the plastic curve 578MPa, Poisson's ratio 0.3, density 7.850kg/m^3 . In order to analyse the interference effect on the fatigue strength some pins made of the same material have been realised. Since the real component has an interference specific level of 0.9%, two different pin diameters were machined: $d=5.03\text{mm}$ and $d=5.1\text{mm}$ in order to obtain a specific interference of 0.6% (low level) and 2% (high level) respectively; the specific interference is calculated as $I\%=(d-D)/D$.

A set of 7 specimens has been tested for each of the three different conditions: i) open hole (OH), ii) low interference level (I06) and iii) high interference level (I2). An additional specimen has been used for the I2 level in order to find the



run out point. Therefore a total of 22 specimens have been realised and tested. The testing machine is a hydraulic press with a load cell of 100kN (frequency up to 25Hz) manufactured by Giuliani s.r.l.. The pins have been press fitted into the plates by the same standing press while standard clamps provided by the press manufacturer have been used to lock the specimens; the pin insertion, the specimen lock system and an example of fracture surface are shown in Fig. 3a, 3b and 3c respectively. The white circle of Fig 3c indicates the starting point of the crack.

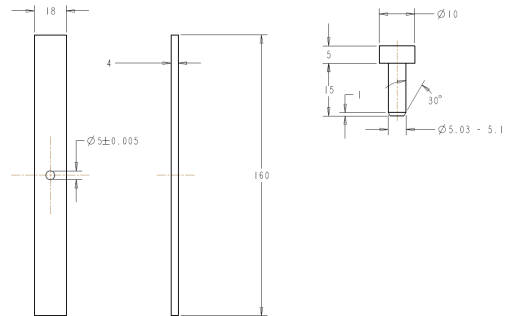


Figure 2: Specimen draft: $K_t=3.31$.

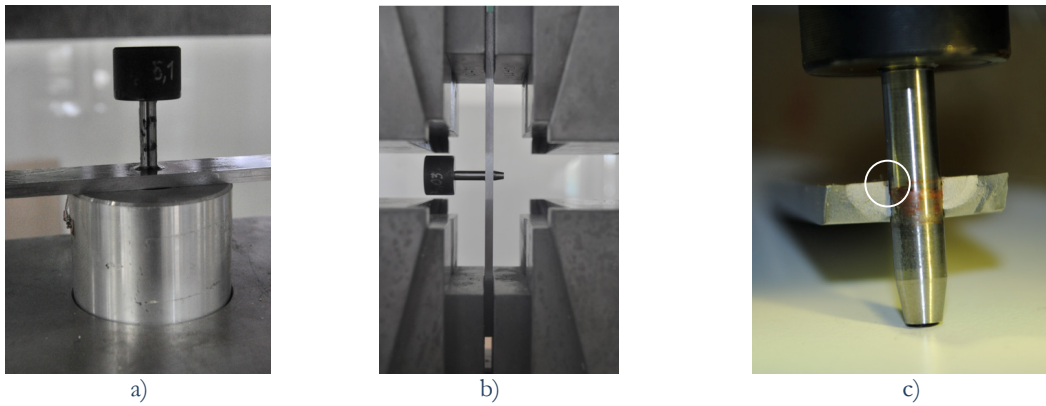


Figure 3: Pin insertion, specimen lock system and fracture surface.

The maximum remote stresses ($RS=F/A$) were set in the range of 725MPa and 200MPa: they have been calculated as the ratio between the external force applied by the standing press and the specimen gross section $A=18*4=72\text{mm}^2$. The *OH* specimens have been tested with steps of 75MPa from 650MPa to 200MPa whereas the *IXX* specimens have been tested with steps of 37.5MPa (from 650MPa to 425MPa for *I06* specimens and from 725MPa to 500MPa plus a single point at 425MPa for *I2* specimens). The stress ratio for all the specimens was set at $R=0.1$.

TESTS RESULTS

The test plan and results are reported in Tab. 1, 2 and 3 for *OH*, *I06* and *I2* respectively, whereas the corresponding *S-N* curves are reported in Fig. 4.

Open Hole	Point # 1	Point # 2	Point # 3	Point # 4	Point # 5	Point # 6	Point # 7
External load (kN)	46.8	41.4	36	30.6	25.2	19.8	14.4
Remote maximum stress (MPa)	650	575	500	425	350	275	200
Cycles	5,897	14,306	21,907	62,105	150,633	252,338	2,000,000 (run out)

Table 1: Stress results for the *OH* specimens.

I06	Point # 1	Point # 2	Point # 3	Point # 4	Point # 5	Point # 6	Point # 7
External load (kN)	46.8	44.1	41.4	38.7	36	33.3	30.6
Remote maximum stress (MPa)	650	612.5	575	537.5	500	462.5	425
Cycles	11,710	98,239	136,289	232,356	684,844	692,557	1,347,271

Table 2: Stress results for the I06 specimens.

I2	Point # 1	Point # 2	Point # 3	Point # 4	Point # 5	Point # 6	Point # 7	Point # 8
External load (kN)	52.2	49.5	46.8	44.1	41.4	38.7	36	30.6
Remote maximum stress (MPa)	725	687.5	650	612.5	575	537.5	500	425
Cycles	35,260	70,017	112,800	136,490	193,510	300,535	430,877	2,000,000 (run out)

Table 3: Stress results for the I2 specimens.

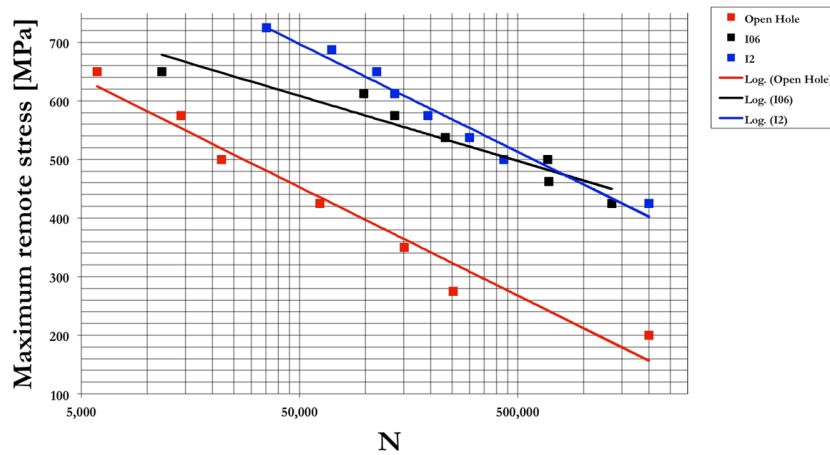


Figure 4: S-N Diagram.

DISCUSSION

Having a look at the S-N diagram reported in Fig. 4, it is possible to confirm that the interference fit level has a strong and positive influence on the fatigue strength of the OH specimen, as widely demonstrated in [5, 7]. Anyway a remarkable difference can be noticed between the two levels, I06 and I2: the more is the interference level, the more is the fatigue strength at the highest levels of remote stress. Conversely, by reducing the remote stress, the fatigue strength and the Endurance Limit is quite the same for different interference levels. This occurrence can be explained by the amplitude of local stress near the hole perturbation. The fracture mechanic of the specimens indicates a crack initiation close to the cross section of the holed surface (see Fig. 3), so that it is easy to imagine that the actual amplitude of axial stress, normal to the cross section of the specimen, produces the crack propagation. The amplitude depends on both the remote stress and the local residual (compressive) stresses due to the Yielding point overcome. For this reason the local amplitude, depending on both the remote stress and the interference level, has been calculated and analysed. Therefore, some Finite Element Analyses (FEA), have been conducted in order to confirm what stated above. In Fig. 5 an example of the FEA model (mesh and contour plot of results) is reported. The analyses are conducted on a 2D elastic plastic plane stress model (6 nodes triangular elements), in which three different steps have been simulated: i) the interference (if present), ii) the application of the maximum remote stress and iii) the unloading with R=0.1. The



actual stress amplitude along the cross section of the specimens, which can be related to fatigue life, has been calculated as the difference between the axial stresses of the phases ii) and iii) and reported in Fig. 6a, 6b and 6c for the *OH*, *I06* and *I2* specimens respectively: the diagrams refer to a remote stress of $RS=357.5\pm 292.5$ (blue curves) and to a remote stress of $RS=233.75\pm 191.25$ (yellow curves) which correspond to a high and low fatigue remote stress respectively.

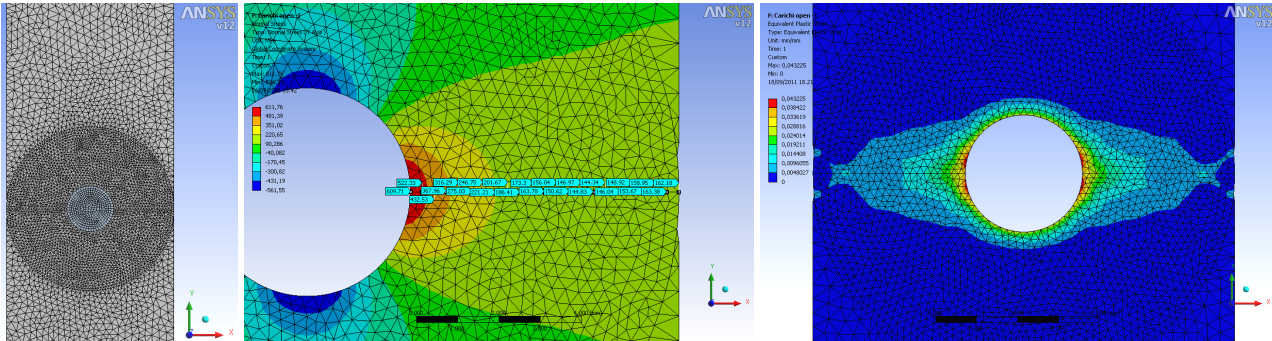


Figure 5: FEA Model.

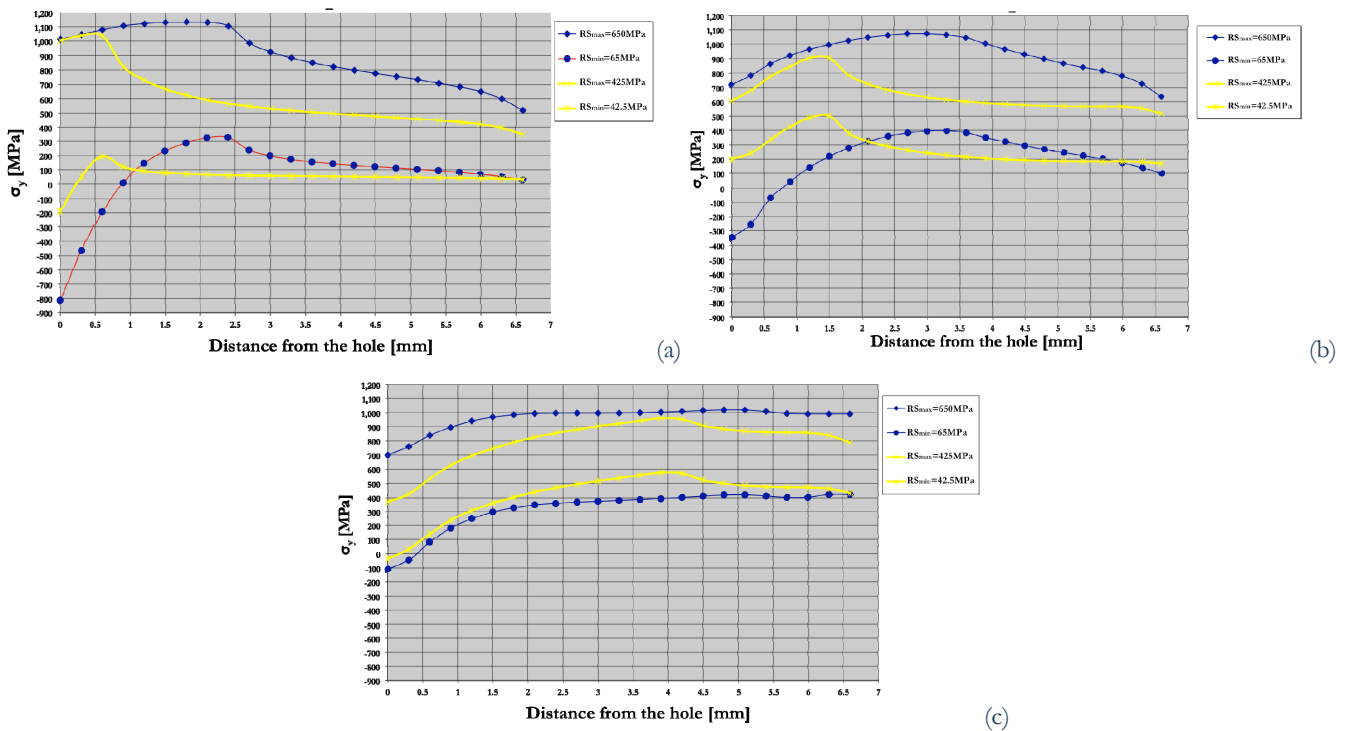


Figure 6: Axial stress amplitude diagrams (Total stress amplitude: a) *OH*; b) *I06*; c) *I2*).

The diagrams of Fig. 6 point out a significant discrepancy among the three actual stress amplitudes, especially when they are calculated close to the hole; the *OH* specimen exhibits a stress amplitude of about 1,800MPa, the *I06* exhibits a stress amplitude of about 1,050MPa and *I2* exhibits a stress amplitude of about 800MPa when $RS=357.5\pm 292.5MPa$ (blue curves of Fig. 6). If the remote stress decreases the discrepancies among actual amplitudes change: the *OH* amplitude remains greater than *I06* and *I2* ones, but the *I06* and *I2* amplitudes tend to become equal. Indeed when $RS=233.75\pm 191.25MPa$ (yellow curves of Fig. 6) the *OH* specimen exhibits a stress amplitude of about 1,200MPa whereas the *I06* and the *I2* specimens exhibit the same stress amplitude of about 400MPa. This is the reason because the fatigue strength of *I06* and *I2* specimens tend to be the same when remote stress decreases. This occurrence is well indicated in Fig. 7 where the stress amplitudes are plotted as a function of the specific interference for different remote stresses: in the diagram of Fig. 6b the stress amplitude at *I06* and at *I2* is, again, the same so that the fatigue strength should be similar;

this event is also confirmed by the S-N diagram of Fig. 4 in which at 425MPa of maximum remote stress the number of cycles reached by *I06* and by *I2* specimens is quite the same. The diagrams of Fig. 7 are also useful to indicate the minimum interference level sufficient to improve the fatigue strength for a stated remote stress; for instance, in the case of $357.5 \pm 292.5 \text{ MPa}$ of remote stress an interference level of 0.6% is enough for increasing the fatigue strength, whereas for $357.5 \pm 292.5 \text{ MPa}$ of remote stress an interference level of about 1% is suggested.

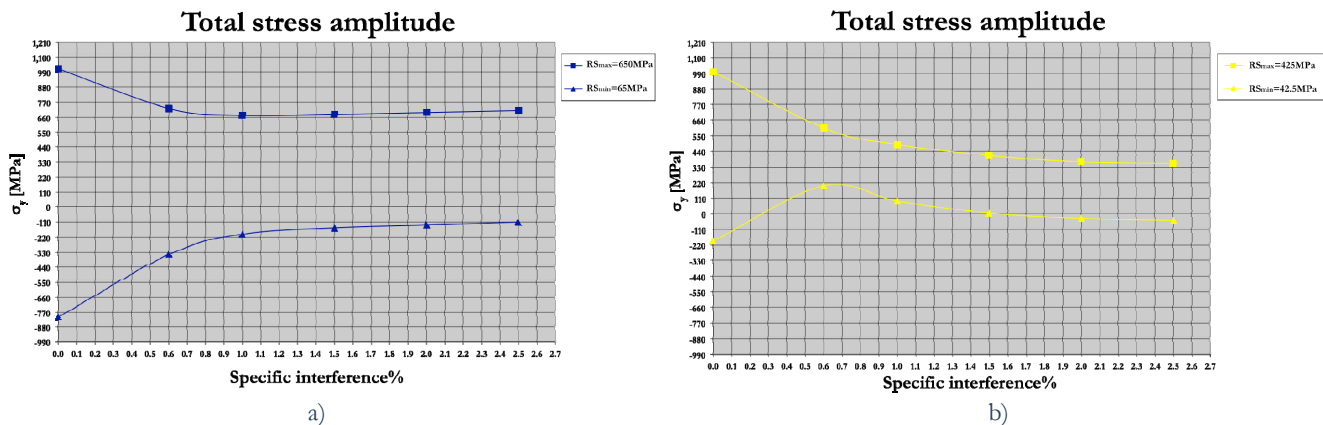


Figure 7: Stress amplitude diagrams.

CONCLUSIONS

In this paper the influence of interference fit coupling on the fatigue strength of holed plates has been investigated both experimentally and numerically. The stress-life curves reported in Fig. 4 highlight a significant difference among the open-hole specimens behaviour and the interference-fit ones. The fatigue strength is always higher when the interference level is higher, anyway since the slopes of the interference fit curves are quite different, the increase of fatigue strength is significant when the remote stress is high; on the opposite the Endurance Limit for both the interference fit levels is quit the same. This event depends on the total stress amplitude, which can be reduced by the interference level up to a minimum value depending on the remote stress; therefore it is not advisable to overcome the interference level, which can guarantee the maximum benefit.

REFERENCES

- [1] D. Croccolo, R. Cuppini, N. Vincenzi, *Finite Elements in Analysis and Design*, 45 (2009) 406.
- [2] D. Croccolo, M. De Agostinis, N. Vincenzi, *Engineering Failure Analysis*, 18 (2011) 364.
- [3] D. Croccolo, M. De Agostinis, N. Vincenzi, *International Journal of Adhesion and Adhesives*, 30 (2010) 359.
- [4] T.N. Chakherlou, M. Mirzajanzadeh, J. Vogwell, *Engineering Failure Analysis*, 16 (2009) 2066.
- [5] A. Lanciotti, C. Polese, *Fatigue Fract Engng Mater Struct*, 28 (2005) 587.
- [6] M. Giglio, M. Lodi, *International Journal of Fatigue*, 31 (2009) 1978.
- [7] T.N. Chakherlou, M. Mirzajanzadeh, B. Abazadeh, K. Saedi, *European Journal of Mechanics A/Solids*, 29 (2010) 675.
- [8] Iyer, K., Rubin, C.A., Hahn, G.T., *J. Tribol-T ASME*, 123 (2001) 686.